

Development of Graphite- and Graphene Reinforced Styrene-Butadiene Rubber

Pirityi Dávid Zoltán,¹ Pölöskei Kornél²

*Budapest University of Technology and Economics, Faculty of Mechanical Engineering,
 Department of Polymer Engineering, Budapest, Hungary*

¹ pirityid@pt.bme.hu

² poloskei@pt.bme.hu

Abstract

The environmental impact of rubber waste can be reduced by extending the lifetime of rubber products. It can be achieved by developing graphene/rubber nanocomposites with good abrasion resistance. In this paper, we investigated how rubber mixing technologies influence the mechanical properties of rubber. We added various amounts (0, 1, 5 and 10 phr) of graphite and graphene to rubber mixtures using a two-roll mill, an internal mixer, a single- and a twin-screw extruder. We performed tensile, tear strength and Shore A hardness tests on the vulcanisates and analysed their fracture surfaces with a scanning electron microscope. Our results show that graphene had a better reinforcing effect than graphite. Rubber mixing via extrusion may contribute to more severe polymer degradation, though their reproducibility is better than that achieved on a two-roll mill or in an internal mixer.

Keywords: *elastomer, graphite, graphene, nanocomposite.*

1. Introduction

Increasingly stringent environmental regulations have put the automobile industry under pressure to minimise the ecological footprint of rubber waste. Two approaches are studied in contemporary material science research: a) recycling (i.e. devulcanisation [1, 2]) and b) extending product life cycle [3, 4]. An excellent way to achieve the latter goal is to develop rubber compounds with increased abrasion resistance. Tyre companies are aiming to replace current tire treads with graphene/rubber nanocomposites [5].

Graphene is the most recently found allotrope of carbon: Noveslov and Geim were awarded the Nobel Prize in Physics in 2010 as an acknowledgement of graphene's first-ever isolation. Graphene is a single atomic layer of graphite with extremely high specific surface area (appx. 2400 m²/g). This property allows graphene to form strong adhesive bonds with organic polymers, making it an excellent reinforcement material in polymer composites [6].

Since most rubber products consist of at least ten ingredients, their structure is rather complex. Consequently, their properties must always be studied holistically. It is practically impossible to improve all mechanical properties simultaneously. Results are satisfactory only if an improvement in one property is not accompanied by such deterioration in others that the product's applicability is compromised [5].

In this paper, we compare the applicability of graphite and graphene in rubber compounds as well as investigating the various effects of mixing technologies.

2. Experimental

2.1. Materials

In this research, we prepared styrene-butadiene rubber (SBR) based compounds to simulate automotive tire treads. The compounds consisted of the following ingredients.

- SBR: SKS-30 ARKPN SBR 1502, an emulsion type SBR base polymer (producer: Synthes Kauchuk JSC, Voronezh, Russia);
- Carbon black (CB): N330 grade amorphous carbon powder (producer: Kremenchug Carbon Black Plant, Kremenchuk, Ukraine);
- Graphene (GR): xGNP Grade H, graphene nanoplatelets (producer: XG Sciences Inc., Lansing, Minnesota, USA);
- Graphite (G): C-Therm graphite with large specific surface area and an average particle thickness of 1 µm (producer: Imerys Graphite & Carbon, Bodio, Switzerland).

To achieve good curing properties, the following materials were added to the compounds: zinc oxide (ZnO), stearic acid, N-cyclohexyl-benzothiazol-2-sulphenamide (CBS), and tetramethylthiuram disulphide (TMTD). Curing agents were supplied by Tauril Kft.

Table 1. shows the composition of rubber mixtures used for the preliminary experiments in parts per hundred rubber (phr). We first prepared the mixtures on a two-roll mill, then analysed the mixing potential of a single-screw extruder at two screw speeds (30 rpm and 120 rpm). The names of the samples include the screw speed, the mixing technology and the type and amount of the nanostructured particles. These parameters are all shown in subscripts: ‘sse’ stands for single-screw extruder, ‘GR1’ means that the mixture contains 1 phr of graphene. Four compounds were prepared: SBR_{ee30}, SBR_{ee120}, SBR_{ee30_GR1}, SBR_{ee120_GR1}.

We based our main experiments on rubber compounds that contained 10 phr of carbon black to achieve better mechanical properties (**Table 2.**) These compounds were also prepared on a two-roll mill, after which they were subjected to further mixing (either in a twin-screw extruder, or in an internal mixer). The nomenclature of these samples conforms to that of the preliminary experiments. Subscripts following ‘SBR’ include the following: ‘tse’, ‘im’, ‘GR’ and ‘G’, meaning twin-screw extruder, internal mixer, graphene, and graphite, respectively. The number at the end of each sample name signifies the amount of particles in phr. The list of samples is as follows: kSBR_{ie}, kSBR_{ie_GR1}, kSBR_{ie_GR5}, kSBR_{ie_GR10}, kSBR_{ie_G1}, kSBR_{ie_G5}, kSBR_{ie_G10}, kSBR_b, kSBR_{b_GR1}, kSBR_{b_GR5}, kSBR_{b_GR10}, kSBR_{b_G1}, kSBR_{b_G5} and kSBR_{b_G10}.

Table 1. Composition of rubber samples in the preliminary experiments

Ingredient	phr
SBR	100
GR	0; 1
ZnO	5
Stearic acid	1
CBS	1
TMDT	0.8
Sulphur	2

Table 2. Rubber compositions used for the main experiments

Ingredient	phr
SBR	100
N330	10
GR	0; 1; 5; 10
G	0; 1; 5; 10
ZnO	3.3
Stearic acid	2
CBS	1.8
TMTD	1.8
Sulphur	1.7

Table 3. The settings of the two-roll mill

Roll:	Roll speed (1/min)		Roll temperature (°C)		Nip gap (mm)
	1.	2.	1.	2.	
0–5 min	3	5	50	70	2
5–10 min	5	8	50	70	0.75
10–15 min	10	15	50	70	0.75

2.2. Technologies

Each rubber compound was premixed for 15 minutes on a Labtech LRM-SC-110/T3E two-roll mill, according to the parameters presented in **Table 3.**

After mixing on the two-roll mill, the preliminary rubber compounds were cut into 10–20 mm wide strips and fed into a Labtech LE 25-30/C single-screw extruder. We were investigating the homogenising effects of extrusion. A temperature ramp was applied over the zones of the extruder. The feed zone was heated to 80 °C and the temperatures were set gradually higher towards the die, which was heated to 100 °C to avoid curing in the extruder.

Similarly to the preliminary experiments, the main experiments also consisted of two mixing steps. After premixing on the two-roll mill, the compounds were either fed to a Labtech LTE 26-44 twin-screw extruder or to a Brabender Plasti-Corder internal mixer. For the twin-screw extrusion, the screw speed was set to 60 rpm and a heat ramp, similar to that used for the single-screw extruder, was applied (80 °C at the feed zone and 100 °C at the extruder die). As for the internal mixer, we equipped it with a 50 cm³ mixing chamber and tangential rotors. The mixer's temperature was set to 70 °C and fill ratio of 70 % was used. Mixing was continued until the melt temperature reached 115 °C.

After mixing, a Collin Pressplate 200E hot press was used to vulcanise the mixtures. 2.7 MPa pressure was applied at 160 °C for t_{90} (until 90 % relative curing was reached). We obtained 2 mm thick rubber sheets, from which we could die cut tensile and tear strength test specimens, using a ball-press.

2.3. Testing

Curing properties of the rubber samples were determined on a MonTech D-RPA 3000 rheometer. We ran the experiments in isothermal time sweep mode at 160 °C with a frequency of 1.67 Hz and an amplitude of 1°. During testing, an uncured piece of rubber mixture is heated up and a continuous oscillating rotary deformation is applied. The rheometer measures the torque (S') needed to maintain the same strain. An increase in torque corresponds with an increase in modulus, thus the degree of curing can be monitored this way.

We performed the tensile tests on a Zwick Z020 tensile tester according to the ISO 37:2017 standard [7] with a 60 mm clamping distance and a 500 mm/min crosshead speed. The same equipment was used to perform tear strength tests, according to the ISO 34-1:2015 standard [8] 500 mm/min crosshead speed and 56 mm clamping distance. A 1 mm cut on each tear strength test specimen was made to ensure the tear would originate from the middle of the specimen.

The fracture surfaces of the torn tensile test specimens were analysed on a JEOL JSM 6380LA scanning electron microscope.

We performed Shore A hardness tests, using a Zwick H04.3150 hardness tester, according to the ISO 48-4:2018 standard [9] taking 10 measurements from each sample.

3. Results

3.1. Preliminary experiments

The tensile and tear strength test results are shown in **Tables 4.** and **5.** respectively. The reinforcement effect of graphene is apparent from both tests at both screw speeds. However, at the slower setting, 1 phr of graphene increased both the tensile strength and the elongation at break by appx. 60%. The faster screw speed had a generally positive influence on material properties: the tensile parameters of the unfilled compound increased significantly, yet SBR_{ee120_GR1} did not match the tensile properties of SBR_{sse30_GR1} . Tear strength results show similar trends: both graphene content and faster screw speed had a positive impact on the tear propagation resistance of the samples.

Based on scanning electron micrographs (**Figure 1**) we concluded that the particle size of graphene did not change due to the faster screw speed of the single-screw extruder. The difference

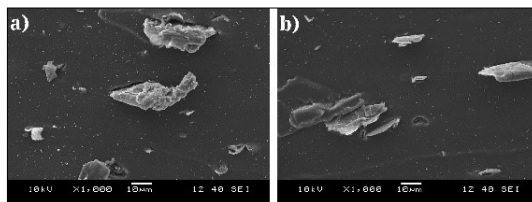


Figure 1. Scanning electron micrographs of the preliminary graphene-containing samples: a) SBR_{ee30_GR1} , b) SBR_{ee120_GR1}

Table 4. Preliminary tensile test results

Sample	Tensile strength (MPa)	Elongation at break (%)
SBR_{ee30}	1.65 ± 0.05	114.3 ± 7.0
SBR_{ee30_GR1}	2.71 ± 0.12	181.9 ± 9.4
SBR_{ee120}	2.08 ± 0.18	164.0 ± 9.7
SBR_{ee120_GR1}	2.30 ± 0.20	158.4 ± 16.3

Table 5. Preliminary tear strength test results

Sample	Tear strength (N/mm)
SBR_{ee30}	4.15 ± 0.17
SBR_{ee30_GR1}	4.29 ± 0.26
SBR_{ee120}	4.40 ± 0.30
SBR_{ee120_GR1}	5.16 ± 0.38

in the tested mechanical properties may be due to the distribution of graphene within the matrix as well as the potential degradation of the polymer chains.

3.2. Comparison of mixing in a twin-screw extruder and in an internal mixer

After preparing the rubber mixtures, we analysed their curing properties. The vulcanisation curves of the twin-screw extruded samples are shown in **Figure 2** and the vulcanisation curves of the samples prepared in the internal mixer are shown in **Figure 3**. We observed a clear trend in **Figure 2**: both the minimum and maximum torque values increased with larger additive contents. This phenomenon indicates that the shear modulus of these rubber compounds increased. The presence of the additive particles decreased the optimal vulcanisation time (t_{90}) by up to 20 % (in the case of SBR_{tse_GR10}) compared to the unfilled compound.

As shown in **Figure 3** the curing properties of the samples prepared in the internal mixer show

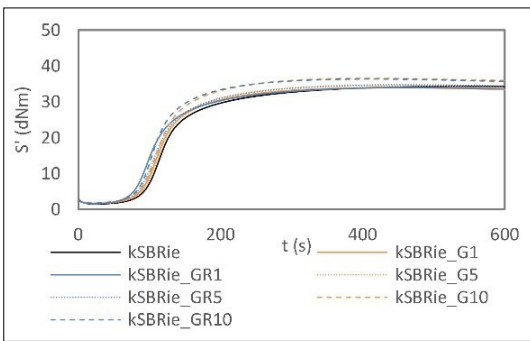


Figure 2. Curing curves of the twin-screw extruded samples

Table 6. Tensile test results for the twin-screw extruded samples

Sample	Tensile strength (MPa)	Elongation at break (%)
kSBR _{ie}	2.87 ± 0.08	120.5 ± 4.1
kSBR _{ie_GR1}	3.30 ± 0.31	128.8 ± 4.5
kSBR _{ie_GR5}	2.75 ± 0.09	114.7 ± 1.0
kSBR _{ie_GR10}	3.82 ± 0.30	125.1 ± 5.8
kSBR _{ie_G1}	2.57 ± 0.17	108.9 ± 8.2
kSBR _{ie_G5}	2.88 ± 0.16	111.5 ± 1.8
kSBR _{ie_G10}	3.24 ± 0.19	115.3 ± 2.1

a larger variation than those prepared in the twin-screw extruder. The sample containing 10 phr of graphite had a strikingly low maximum torque value. This property normally shows good correlation with the hardness and modulus of rubber compounds. Consequently, we expected SBR_{im_G10} to have the lowest hardness among this experimental set. In contrast, it was the hardest sample prepared in the internal mixer (**Figure 5**).

The tensile test results for the samples prepared in the twin-screw extruder and the internal mixer are summarized in **Tables 6** and **7** respectively.

Our main objective was to identify the differences in the reinforcement capabilities of graphene and graphite at various concentrations. According to **Table 6**, the use of graphene resulted in better mechanical properties than the use of graphite. The tensile strength of SBR_{tse_GR1} almost matched that of SBR_{tse_G10} , meaning that 1 phr of graphene content is equivalent to 10 phr of graphite content. In summary, the best mechanical properties were achieved with a 10 phr graphene content. The tensile strength of SBR_{tse_GR1} was 30 % larger than that of the unfilled sample.

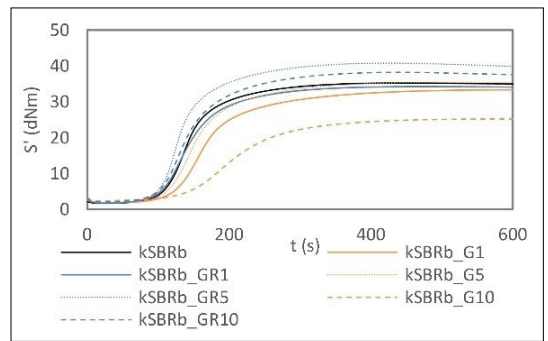


Figure 3. Curing curves of the samples prepared in the internal mixer

Table 7. Tensile test results for the samples prepared in the internal mixer

Sample	Tensile strength (MPa)	Elongation at break (%)
kSBR _b	1.60 ± 0.03	79.6 ± 7.2
kSBR _{b_GR1}	1.27 ± 0.06	65.3 ± 10.6
kSBR _{b_GR5}	3.05 ± 0.06	92.6 ± 4.9
kSBR _{b_GR10}	3.96 ± 0.08	162.5 ± 18.6
kSBR _{b_G1}	1.76 ± 0.04	93.2 ± 6.7
kSBR _{b_G5}	2.49 ± 0.07	91.8 ± 2.0
kSBR _{b_G10}	2.54 ± 0.08	76.4 ± 1.9

The tensile properties of the samples prepared in the internal mixer (Table 7) were considerably poorer than those of the extruded samples. Only one of the samples surpassed 100% relative elongation: SBR_{im_GR10} . This single sample outperformed all other samples, including the extruded compounds. This dual behaviour may be explained by two factors: a) the low repeatability of mixing in the internal mixer, and b) the potential polymer degradation in the twin-screw extruder (causing the lower maximum values).

The tear strength of all experimental samples versus their respective additive content is plotted in Figure 4. Samples that had been prepared in the internal mixer outperformed those prepared in the extruder significantly. SBR_{im_GR10} showed outstanding tear strength in comparison with all other samples. This phenomenon further supports that better properties are attainable in the internal mixer, due to the polymer degradation during extrusion.

The Shore A hardness of the samples is shown in Figure 5. It is evident that increasing additive content resulted in higher Shore A hardness, regardless of the type of mixing and type of nanostructured additive. There was a single outlier, SBR_{tse} , its hardness surpassed that of the samples with 5 phr nanostructured additive content.

We analysed the morphology of the composites via scanning electron microscopy. The most revealing micrographs are presented in Figure 6. We selected the images to represent the fracture surface as closely as possible. The layered structure of both graphene and graphite is clearly visible, but graphite had a higher number of distinguishable layers. Graphene particles seem to have stayed intact, protruding out of the fracture surface. In contrast, graphite layers seem to have undergone some deformation, creating more irregularities in the system. Samples that had been prepared via extrusion contained thin fibrils that made the adhesion between the nanostructured additive particles and the rubber matrix stronger. The distribution of the additive particles appears to be better in the extruded samples.

4. Conclusions

During our preliminary experiments, we showed that graphene can significantly improve the mechanical properties of rubber compounds even at small (1 phr) concentration.

The main experiments revealed that better distribution of the nanostructured additive particles

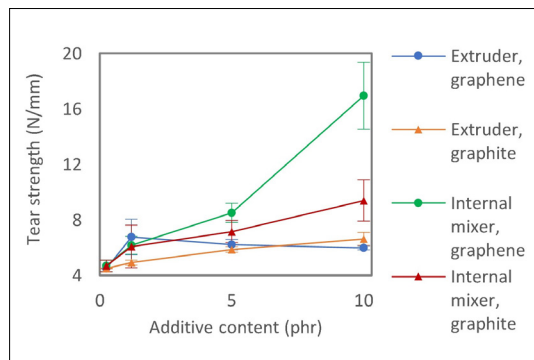


Figure 4. Tear strength of the rubber composites vs. their additive content.

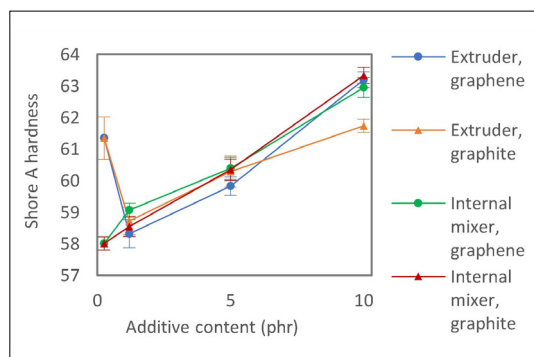


Figure 5. Shore A hardness of the prepared rubber composites vs. their additive content.

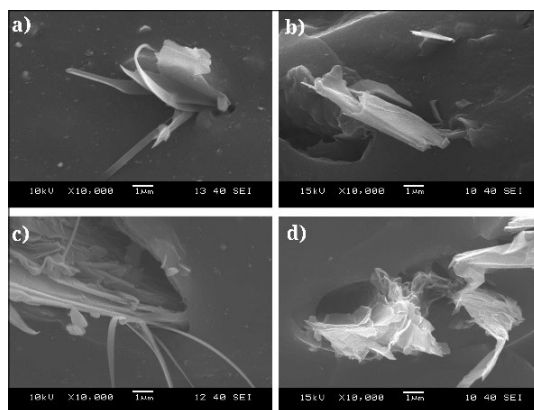


Figure 6. Scanning electron micrographs of the fracture surfaces of tensile test specimens: a) $kSBR_{ie_GR10}$ b) $kSBR_{b_GR10}$ c) $kSBR_{ie_G10}$ d) $kSBR_{b_G10}$

is attainable via twin-screw extrusion, compared to preparation in an internal mixer. Despite this, the compounds prepared in the internal mixer outperformed the extruded samples in terms of

hardness and tear strength. A possible explanation is that extrusion might have caused some polymer degradation due to more intense shearing.

Altogether, the future development of graphene-reinforced rubber compounds has great potential. The effects of mixing technologies should be studied more deeply to reach clear conclusions.

Acknowledgement

The research reported in this paper and carried out at BME has been supported by the National Research, Development and Innovation Office, Hungary (2017-2.3.6-TÉT-CN-2018-00002). Hereby, we would like to thank Szilvia Mórítz for her help with the execution of the experimental work.

References

- [1] Formela K., Hejna A., Zedler Ł., Colom X., Cañavate J.: *Microwave treatment in waste rubber recycling - recent advances and limitations*. Express Polymer Letters, 13. (2019) 565–588.
<https://doi.org/10.3144/expresspolymlett.2019.48>
- [2] Kaewpetch B., Prasongsuk S., Poompradub S.: *Devulcanization of natural rubber vulcanizates by Bacillus cereus TISTR 2651*. Express Polymer Letters, 13. (2019) 877–888.
<https://doi.org/10.3144/expresspolymlett.2019.76>
- [3] Cao L., Sinha T. K., Tao L., Li H., Zong C., Kim J. K.: *Synergistic reinforcement of silanized silica-graphene oxide hybrid in natural rubber for tire-tread fabrication: A latex based facile approach*. Composites Part B: Engineering, 161. (2019) 667–676.
<https://doi.org/10.1016/j.compositesb.2019.01.024>
- [4] Hajba S., Tábi T.: *Cross effect of natural rubber and annealing on the properties of poly(lactic acid)*. Periodica Polytechnica Mechanical Engineering, 63. (2019) 270–277.
<https://doi.org/10.3311/PPme.12825>
- [5] Guo H., Ji P., Halász I. Z., Pirityi D. Z., Bárány T., Xu Z., Zheng L., Zhang L., Liu L., Wen S.: *Enhanced fatigue and durability properties of natural rubber composites reinforced with carbon nanotubes and graphene oxide*. Materials, 13. (2020) 5746.
<https://doi.org/10.3390/ma13245746>
- [6] Berki P., László K., Tung N. T., Karger-Kocsis J.: *Natural rubber/graphene oxide nanocomposites via melt and latex compounding: Comparison at very low graphene oxide content*. Journal of Reinforced Plastics and Composites, 36. (2017) 808–817.
<https://doi.org/10.1177/0731684417690929>
- [7] ISO 37:2017: Rubber, vulcanized or thermoplastic – Determination of tensile stress-strain properties, 2017.
- [8] ISO 34-1:2015: Rubber, vulcanized or thermoplastic – Determination of tear strength – Part 1: Trouser, angle and crescent test pieces, 2015.
- [9] ISO 48-4:2018: Rubber, vulcanized or thermoplastic – Determination of hardness – Part 4: Indentation hardness by durometer method (Shore hardness), 2018.